

## An Experimental Study on the Properties of SCC with Manufactured Sand

Deep Tripathi<sup>a\*</sup>, Rakesh Kumar<sup>b</sup>, P. K. Mehta<sup>c</sup> and Vishal Rawat<sup>d</sup>

<sup>a</sup>Research Scholar, <sup>b,c</sup>Professor, <sup>d</sup>M.Tech. Student

M.N.N.I.T. Allahabad, Prayagraj (UP), India- 211004

\*E-mail: drt.ald10@gmail.com/deep@mnnit.ac.in

*Manuscript Received online 7/3/2020, Accepted 10/29/2020*

The findings of a study on Self Compacting Concrete (SCC), made using natural and manufactured sand (M-sand) are presented. The referral SCC (M25) was made by substituting a part (20%) of Ordinary Portland Cement (OPC) with Class-F Fly Ash (FA). The other SCCs were made by replacing parts of natural sand (NS) with M-sand, by mass. The workability parameters of SCCs in fresh state were determined as per the recommendations EFNARC-2005. The specimen of both SCCs were cast and tested for important strength parameters at different ages as per Indian Standards. It is found that 50% of NS can be replaced by M-sand. The specimen's water absorption was also studied up to 90 days.

Keywords: Ordinary Portland Cement, SCC, Workability, M-Sand, FA

### Introduction

The use of SCC is increasing and gaining popularity the world over. Its composition is different than the normal concrete mixes and it utilizes a lot of fines which consists of sand and other pozzolanic materials. In view of the increasing natural and global consensus on the environmental protection, the governments have put restrictions on mining of natural sand from river beds. The M-sand may supplement/fulfil the shortage of natural sand.

Ramanathan et al.<sup>1</sup> stated that the properties of SCC made by replacing 30% of OPC with FA. It is also stated that the loss of compressive strength (CS) and water absorption are decrease with increase in FA content. Gaywala et al.<sup>2</sup> stated that SCC's compressive, split-tensile, flexural and pull out strengths were maximum at 15% replacement level of OPC with FA. Water absorption increases with FA content although it decreases with an increase in the curing period<sup>3</sup>. FA is considered to be the most appropriate pozzolana for sustainable SCC production<sup>4</sup>. 50-60% FA can be included in SCC to improve workability parameters with a substantial increase in CS are observed up to 180 days<sup>5</sup>. The

addition of pozzolanas has positive effect on the properties of SCC compared to normally vibrated concrete (NVC)<sup>6</sup>. The FA exhibits ball bearing effect due to which the dose of plasticizer is decreased and self-compactability is substantially improved<sup>7</sup>. The addition of FA in SCC forms additional C-S-H gel in long term, specially after 56 days, and results in an increase in CS<sup>8</sup>. SCC incorporating mineral admixtures reduces water absorption due to improved pore structure<sup>9</sup>. M-sand has been used successfully as a filler material for preparing SCC. Its use improves the hardened properties and reduces the environmental impact also<sup>10</sup>. The CS of SCC containing mineral admixtures is more than the normal SCC<sup>11, 12</sup>. For the same paste composition, the CS of M-sand mixed concrete is more than that containing natural sand only<sup>13</sup>. The use of M-sand containing no more than 13% stone powder content has been reported to be advantageous for the long-term split-tensile strength (STS) of M-sand concrete<sup>14</sup>.

This work compares different SCCs with and without M-sand. The SCC was prepared using supplementary cementations material FA. For partial substitution of the fine aggregate, M-sand was used. For preparing the SCCs, 20% of OPC was substituted

by FA on equal weight basis, and fine aggregate was replaced by M-sand on equal weight basis (10, 20, 30, 40, 50 and 60%). The cubes (size-100mm), cylinders (size-100mm×200mm) and beams (size-100mm×100mm×500mm) were cast for CS, STS and flexural strength (FS), respectively. The cast specimens were tap-water cured and tested at 7, 28, 56 and 90 days. The weights of the samples were measured at different time intervals for determining the water absorption.

### Experimental Study

#### Raw Materials and Their Properties

For development of this research, a 43 grade OPC (Brand-MP Birla), confirming to IS: 8112-1989, was used. Rounded NS falling in Zone II of IS: 383-1970 was used. The other important properties of the NS are: Specific gravity- 2.65; Fineness modulus- 2.7; Bulk density- 1680 kg/m<sup>3</sup>. The Bulk density; Specific gravity and Fineness modulus of M-sand are 1744 kg/m<sup>3</sup>, 2.72 and 3.08, respectively. M-sand was procured from Jhansi, UP, and it also satisfied the requirements of Zone-II. The properties of 10 and 20 mm coarse aggregates are given in order: Specific gravity- 2.66 and 2.7; Water absorption- 1.0 and 0.9%; Fineness modulus- 6.7 and 7.2; Bulk density- 1590 and 1560 kg/m<sup>3</sup>. The above values satisfy the requirements of IS 383-1970. The FA (Class-F; Colour- grey; Specific gravity- 2.13), satisfying the requirements of IS 3812-2000, was purchased from NTPC-Unchahar (UP). A Master Rheobuild 817RL Superplasticizer based on polycarboxylic ether with a density of approx. 1.08 was used. The distribution of the particle size of both the NS and M-sand is presented in Fig. 1. Table 1 presents the constituents of both OPC and FA.

M25 grade SCC mix was prepared in this study using 43 grade OPC, satisfying the requirements of EFNARC, 2005. The quantities of different materials in 1 cubic meter of SCC at Water/binder ratio- 0.43 was: Binder content- 450 Kg; Sand- 890 Kg; Coarse Aggregate- 750 Kg; Superplasticizer- 4.95 Kg.

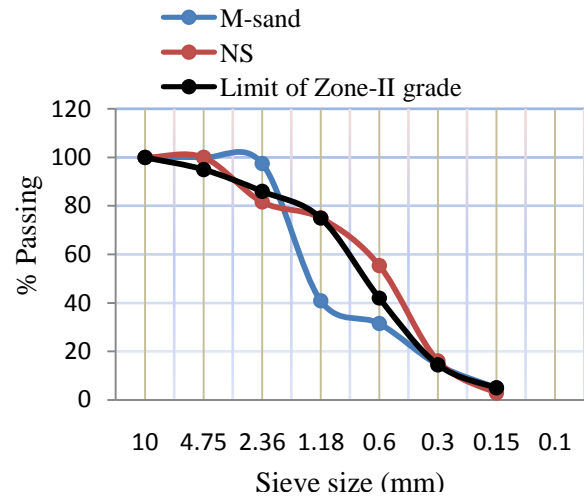


Fig. 1. Distribution of Particle size of both NS and M-sand

Table 1. Constituents of OPC and FA

Chemical Composition (%)	OPC	FA
Silicon dioxide (SiO <sub>2</sub> )	20.05	55.40
Aluminum oxide (Al <sub>2</sub> O <sub>3</sub> )	61.95	4.19
Iron oxide (Fe <sub>2</sub> O <sub>3</sub> )	4.12	6.82
Magnesium oxide (MgO)	2.77	2.02
Potassium oxide (K <sub>2</sub> O)	0.94	1.93
Sodium oxide (Na <sub>2</sub> O)	0.25	0.62
Loss of ignition	3.11	2.40

A part of OPC (20%) was replaced with FA (by mass) for making all SCC specimens. For determining the optimum dose of M-sand in SCC, NS was replaced at different levels (10-60%, by mass, interval-10%) with M-sand. Two type of SCC mixes were prepared and are designated as M-1 (SCC without M-sand) and M-2 (SCC with M-sand). The tests performed for determination of the fresh properties are: Slump flow; T50 time; V-funnel; L-box; U-box and J-ring.

Table 2 presents mixture proportions, water/binder ratio and fresh properties. Cubes, cylinders and beams of both M-1 and M-2 type SCC were cast to assess their strengths in compression,

tension and flexure. The water cured specimens were tested at 7, 28, 56 and 90 days. The cubical and cylindrical specimen were tested following the specifications of IS: 516-1959 and IS: 5816-1999, respectively. The FS was determined using a two point method as per requirements of IS: 516-1959.

**Table 2.** Mixture composition of SCCs

Mix properties	M-1 type	M-2 type
w/b ratio	0.44	0.44
OPC (kg/m <sup>3</sup> )	360	360
Fly Ash (kg/m <sup>3</sup> )	90	90
Coarse Aggregate (kg/m <sup>3</sup> )	750	750
Fine Aggregate (kg/m <sup>3</sup> )	890	445
M-sand (kg/m <sup>3</sup> )	---	445
Water (kg/m <sup>3</sup> )	190	190
Superplasticizer (kg/m <sup>3</sup> )	4.95	4.95

#### Optimization of M-sand

After 7 and 28 days of tap-water curing, the CS of all the cubes were determined to find the optimum M-sand level and the results are presented in Table 3. The optimum dose of M-sand was found to be 50% (by mass), with respect to CS.

**Table 3.** CS of specimens at various M-Sand levels

Replacement level (%)		CS (MPa)	
M-1 type	M-sand	7 days	28 days
20%FA	0	25.00	32.33
20%FA	10	26.67	33.00
20%FA	20	27.33	34.67
20%FA	30	28.67	35.00
20%FA	40	29.33	36.67
20%FA	50	30.67	38.33
20%FA	60	29.00	35.33

## Results and Discussion


#### Workability Parameters of SCC

The values of all the workability parameters for both the mixes i.e. M-1 and M-2 type are given in Table 4. Further, these values are shown in Figs. 2-4


for different mixes with varying percentages of M-sand. Table 4 indicates that the fresh properties of M-2 mixes are influenced by the replacement of the NS with M-sand, but the test results are within the EFNARC limits.

**Table 4.** Test parameters of Fresh Concrete for both mix types


Tests	M-1 type	M-2 type
Slump flow (mm)	720	695
T <sub>50</sub> time (sec)	3	4.2
V- funnel (sec)	10	11.2
L- box (h <sub>2</sub> /h <sub>1</sub> )	0.96	0.87
U- box (mm)	17	22
J-ring (mm)	6	8

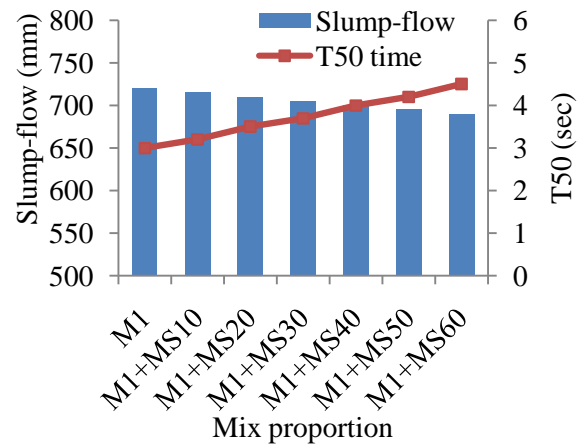

**Fig. 2.** Variation of Slump-flow and T<sub>50</sub> time of different mixes

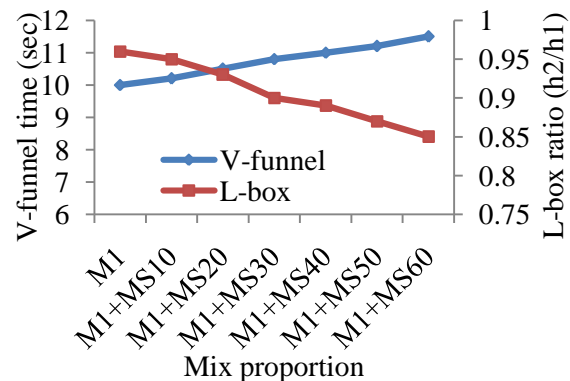

**Fig. 3.** Variation of V-funnel time and L-box ratio of different mixes

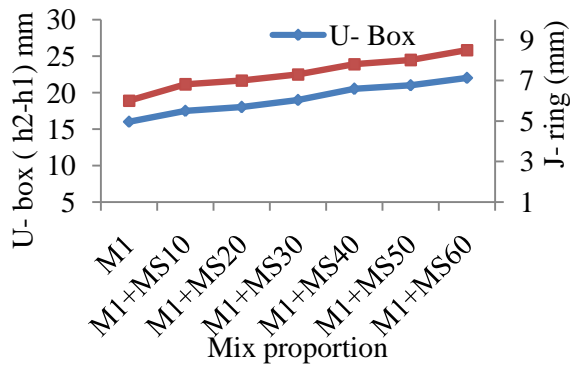


**Fig. 4.** Variation of U- box and J- ring values of different mixes

#### Hardened Properties of SCC

##### Compressive Strength (CS)


Fig. 5 shows the variation of CS for both M-1 and M-2 type mixes. The CS of type M-1 SCC at 7 days is around 25.0% lower than that of M-2. The CS of M-2 mix was found to be 11.93, 15.78 and 17.53 % higher at 28, 56 and 90 days, respectively. With age, the difference in the CS of the two mixtures is found to increase. This increment may be due to M-sand mixed concrete's optimized pore structure.

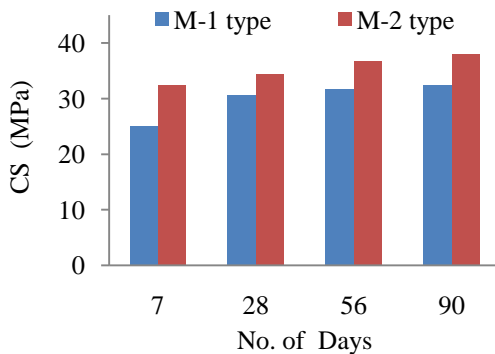

**Fig. 5.** CS of the specimens

##### Split-tensile Strength (STS)


The variation of STS for both mixes (M-1 and M-2 type) is shown in Fig. 6. The M-1 type SCC has about 11.0% lower STS at 7 days compare to the M-2 type. The STS of the M-2 type is found to be 24.67, 16.60 and 13.58 % higher at 28, 56 and 90 days, respectively.

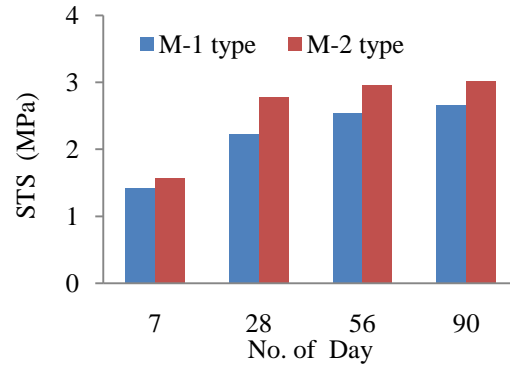

**Fig. 6.** STS of the specimens

##### Flexural Strength (FS)


The results of the FS test is performed on different mixes (M-1 and M-2 type) are shown in Fig. 7. The M-1 type has about 8.50% lower flexural than the M-2 type at 7 days. At 28, 56 and 90 days also, it is found to be higher for M-2 type by 8.29, 6.76 and 5.87%, respectively.

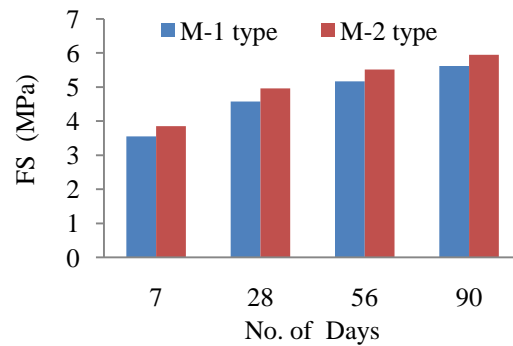

**Fig. 7.** FS of the specimens

##### Water Absorption

For both M-1 and M-2 type mixes, the water absorption values are included in Fig. 8. It's obvious from Fig. 8 that M-2 type's water absorption is lower than that of the M-1 type. Besides that, it is reported that both NVC and SCC show lower water absorption with a rise in age<sup>15</sup>. The FA and M-sand act as a filler material and help in reduction of water absorption. M-2 type's water absorption is found to be 17.53, 13.72, 11.94 and 9.71% lower than the M-1 type at 7, 28, 56 and 90 days, respectively. Other researchers have also reported the same pattern<sup>3</sup>.

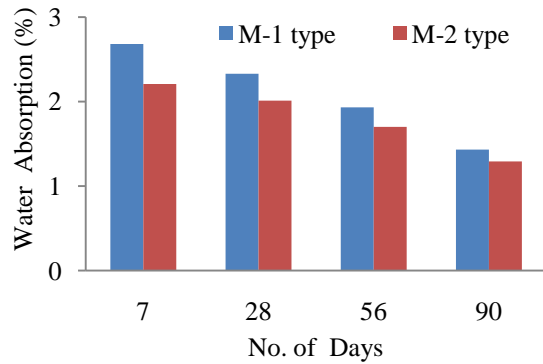

**Fig. 8.** Water Absorption of specimens

## Conclusions

The following are concluded from the detailed investigation.

- The workability and/or flowability of SCC mix decrease slightly as M-sand content increases; however, these are within the EFNARC limits.
- The optimum dose of M-sand in SCC is 50% with respect to compressive strength.
- All the strength parameters improve significantly on addition of M-sand at optimum level.
- The water absorption and pore spaces in SCC decrease significantly on inclusion of M-sand.

## References

1. S Dhiyaneshwaran, P Ramanathan, I Baskar, R. Venkatasubramani, Study on durability characteristics of self-compacting concrete with fly ash, *Jordan Journal of Civil Engineering*, 2013, **7**, 342-52.
2. J. M. Khatib, Performance of self-compacting concrete containing fly ash, *Construction and Building Materials*, 2008, **22**, 1963–1971.
3. NR Gaywala, DB Raijiwala, Self compacting concrete: A concrete of next decade, *Journal of Engineering Research & Studies*, 2011, **2**.
4. MK Mohammed, AR Dawson, NH Thom, Production, microstructure and hydration of sustainable self-compacting concrete with different types of filler, *Construction and Building Materials*, 2013, **1**, 84-92.
5. De Matos, Paulo Ricardo, Maiara Foiato, and Luiz Roberto Prudêncio Jr, Ecological, fresh state and long-term mechanical properties of high-volume fly ash high-performance self-compacting concrete, *Construction and Building Materials*, 2019, **203**, 282-293.
6. Güneyisi, Erhan, Mehmet Gesoğlu, Emad Booya, and Kasim Mermerdaş, Strength and permeability properties of self-compacting concrete with cold bonded fly ash lightweight aggregate, *Construction and Building Materials*, 2015, **74**, 17-24.
7. Puthipad, Nipat, Masahiro Ouchi, Sovannasathya Rath, and Anuwat Attachaiyawuth, Enhancement in self-compactability and stability in volume of entrained air in self-compacting concrete with high volume fly ash, *Construction and Building Materials*, 2016, **128**, 349-360.
8. B. Mahalingam, K. Nagamani, L. S. Kannan, K. Mohammed Haneefa, and A. Bahurudeen, Assessment of hardened characteristics of raw fly ash blended self-compacting concrete, *Perspectives in Science*, 2016, **8**, 709-711.
9. Deep Tripathi, Rakesh Kumar, P.K. Mehta, Amrendra Singh, Optimum Dose of Binary Admixture in Self Compacting Concrete, *International Journal of Innovative and Exploring Engineering*, 2019, **9**, 103-108.
10. Prakash Nanthagopalan, Manu Santhanam, Fresh and Hardened Properties of Self Compacting Concrete Produced with Manufactured Sand, *Cement and Concrete Composites*, 2011, **33**, 353-358.
11. Deep Tripathi, Rakesh Kumar, P. K. Mehta and Amrendra Singh. Silica Fume Mixed Concrete in Acidic Environment, *Materials Today: Proceedings*, 2020, **27**, 1001-1005.
12. Amrendra Singh, Rakesh Kumar, P. K. Mehta and Deep Tripathi, Effect of Acidic Environment on Rice Husk Ash Steel Fibre Reinforced Concrete, *Materials Today: Proceedings*, 2020, **27**, 995-1000.
13. Weiguo Shen, Zhenguo Yang, Lianghong Cao, Liu Cao, Yi Liu, Hui Yang, Zili Lu and Jian Bai, Characterization of manufactured sand: Particle shape, surface texture and behavior in concrete, *Construction and Building Materials*, 2016, **114**, 595-601.
14. Shunbo Zhao, Xinxin Ding, Mingshuang Zhao, Changyong Li and Songwei Pei, Experimental

study on tensile strength development of concrete with manufactured sand, *Construction and Building Materials*, 2017, **138**, 247-253.

15. Deep Tripathi, Rakesh Kumar, P. K. Mehta, Amrendra Singh, A Comparative Study of Normal and Self-compacting Concrete (Adhikari S., Dutta A., Choudhury S.) *Advances in Structural Technologies*, Springer Nature, Singapor, 2020, **11**, 133-143.